



Effects of Macro-Synthetic Fibres Incorporation on the Dimensional Change Properties of Bacillus Subtilis Bacterial Concrete

Ghoniem, A.G.^{1*}, Aboul Nour, L.² and Hassan, H.²

¹ Ph.D., Instructor, Structural Engineering Department, Faculty of Engineering, Zagazig University, Egypt.

² Professor, Structural Engineering Department, Faculty of Engineering, Zagazig University, Egypt.

© University of Tehran 2024

Received: 21 Dec. 2023;

Revised: 14 Mar. 2024;

Accepted: 29 May 2024

ABSTRACT: Immediate dimensional changes during loading are critical characteristics that must be thoroughly understood to ensure the long-term durability and performance of concrete. In the current study, the effects of fixed bacterial content and different macro-synthetic fibre mechanical properties and fibre percentages on concrete dimensional changes were evaluated using 34 mixed designs. The influence of low- and high-strength macro-synthetic fibre with nine contents ranging from 0% to 4% on M40 concrete was investigated with and without calcium carbonate precipitation of *Bacillus subtilis* activity at a cell concentration of 105 cells/ml. The ANSYS package was used to compute the homogenized properties of the composite materials, such as the elastic modulus, shear modulus, and Poisson's ratio. For validation, the numerical results showed good agreement with the analytical results of the dilute distribution model and the Mori-Tanaka model. Compared to the reference conventional concrete, the results showed that adding bacteria and 2% high-strength macro-synthetic fibre simultaneously improved elasticity, shear moduli, and Poisson's ratio by 17.89%, 15.16%, and 3.30%; however, low-strength macro-synthetic fibres caused 3.54%, 1.32%, and 2.98% reduction, respectively. Overall, high-strength macro-synthetic fibre improves the properties of bacterial concrete composite for a variety of structural applications when compared to other traditional concrete.

Keywords: Composite Materials, Elasticity and Shear Moduli, Numerical Homogenized Simulation, Poisson's Ratio, Polyethylene Fibre.

1. Introduction

Conventional Concrete (CC) cracks can lead to steel reinforcement corrosion; however, Bacterial Concrete (BC), also known as self-healing concrete, offers a solution by using bacteria to repair cracks and enhance the properties of fibre concrete (Chithambar Ganesh et al., 2019). The sustainable immediate self-repair of the

formed micro- and macro-cracks can prevent crack growth by limiting the paths for liquids and gases that may contain harmful chemical substances (Hameed et al., 2023). Biogenic origins, such as ureolytic bacteria, can induce CaCO_3 precipitation, leading to the self-healing of cracks in concrete when exposed to different environmental conditions or

* Corresponding author E-mail: agghoneim@zu.edu.eg

mechanical loads (Rameshkumar et al., 2020). *Bacillus subtilis* embedded in BC can repair cracks and restore the original mechanical properties of concrete for up to 200 years (Jena et al., 2020). *Subtilis* can repair a cement mortar crack width of 0.3 mm within 1-5 days in the laboratory (Vijay et al., 2017) and may take several weeks for the total rehabilitation of the macro-cracks up to 0.46 mm (Wiktor and Jonkers, 2011) or 0.5 mm (Wang et al., 2014). This self-healing increased the compressive strength f_c' by an average value of 23% at 28 d, and the split tensile strength f_t improved in the range of 13.7 - 25.3% (Ghoneim et al., 2020). Moreover, self-healing can reduce porosity, increase durability, guarantee a reduction in degradation rates, lower repair frequency, minimize the costs of strength monitoring/damage detection, and extend the ultimate service life of concrete structures (Alshalif et al., 2020; Bhaskar, 2021). Incorporating fibres in concrete, which serve as reinforcement, improves the self-healing performance by bridging cracks and reducing the amount of healing product required (Zhang et al., 2020).

Calcite sediment remediation techniques can fill inaccessible concrete pores caused by the use of fibres in concrete. Polypropylene fibres can prevent cracking, thereby affecting the dimensional changes and quality of the material (Tiwari and Singh, 2024). The dimensional stability of concrete depends on the environmental conditions and applied loads; however, it is also related to the concrete mix components. This study demonstrates the effectiveness of a dual-component composite material consisting of randomly distributed fibres and bacteria in immediate elastic dimensional changes related to the applied loading of concrete. Because of their ease of application, low density, and non-breakability, synthetic fibres have been commonly considered for use in concrete.

Macro fibres are defined as fibres with a diameter greater than 0.3 mm and a specific surface area of approximately 10 cm²/g (Jawhar et al., 2024). Increasing the

fibre content in Fibre-Reinforced Concrete (FRC) to 4% strikes a balance between achieving maximum strength and maintaining workability (Hasan et al., 2019), while also improving ductility and toughness (Yoo and Moon, 2018). In addition, Fibre-Reinforced Bacterial Concrete (FRBC) is a composite material with greater stability over shelf-life and multiple significant environmental footprints. In the last 10 years, the major advantages of FRBC have been investigated by many researchers, as follows: i) Crack bridging recovery, as provided by ESEM/XEDS microscopic images (Feng et al., 2019); ii) Improving healing participation to fill the crack-controlled width pattern (Qian et al., 2009); iii) Enhancing the ultimate load capacity and ductility (Hao et al., 2018; Ghoniem et al., 2021); iv) Enhancing fibrous concrete porosity and extending the service life of the structure (Kua et al., 2019; Karimi and Mostofinejad, 2020); (v) Recycling nonbiodegradable thermoplastic materials in fibrous concrete is an environmentally safe procedure (Merli et al., 2019).

Understanding the concept of dimensional change in synthetic fibrous bacterial concrete requires an exploration of how fibres contribute significantly to the overall properties of the material, including reducing shrinkage and enhancing toughness, crack resistance, and flexural strength (Amjad et al., 2023; Damodaran and Thangasamy, 2023). Hence, the elastic dimensional change of synthetic fibrous bacterial concrete is a multifaceted topic that requires a thorough understanding of the composition of the material, the effects of synthetic fibres on bacterial activity, and influencing factors. The dimensional change properties have scarcely been investigated from a numerical analysis point of view to avoid time-consuming laboratory experiments. The main issue of numerical simulation is that the synthetic fibre diameter is a few micrometers, while the structural dimension is in meters.

Therefore, the mechanical properties of

such composites are a multiscale modelling problem (Geers et al., 2010; Montero-Chacón et al., 2019). There are two approaches to the numerical simulation of composite structures. 1) The hierarchical approach is called the FE2 approach because there is a separate microscopic finite element simulation for every integration point of the macroscopic Finite Element (FE) simulation. The stress and strain are computed in the smaller length scale, and the averaged values are sent back to the larger length scale (Raju et al., 2021).

2) The homogenization approach is called the unit cell approach, as it is the most popular approach to eliminate the scale problem in FE2 analysis. The homogenization/unit cell approach for composite structure simulation has been described in the literature, in which the composite properties were averaged based on microstructure analysis rather than simulating the entire complex microstructure. Full-field approaches, based on periodic homogenization theory, estimate the overall behavior of an equivalent homogeneous material by defining a Repeated/representative Volume Element (RVE) (Naili et al., 2020). An equivalent inclusion Dilute Distribution (DD) model can predict the effective bulk modulus K_{eff} and shear modulus G_{eff} of a composite in which a single inclusion/fibre is in an infinite elastic host material matrix (Eshelby, 1957). The DD model is more suitable for small volume fractions of inclusions, where interactions between inclusions are negligible as they are far apart. Another widely used model is the Mori-Tanaka (MT) model, which is very close to the experimental results for the prediction of the effective bulk modulus and shear modulus. The MT model, based

on the average matrix stress assumption, imposes an additional condition on the DD model to consider the effect of multiple inclusions by combining the DD theory with the effective field concept (Benveniste, 1987). The current study numerically investigated the composite properties by considering the unit cell approach of the composite structure simulated by ANSYS material designer as an integrated component system in the ANSYS software package. The elastic modulus, shear modulus, and Poisson's ratio were estimated to explore the synergistic effects of bacteria and fibres.

The effects of high- and low-strength macro-synthetic fibres introduced by different volumes on the properties of concrete incorporating *Bacillus subtilis* bacteria at a concentration of 105 cells/ml in mixing water were evaluated. Finally, the gradual changes in the material properties obtained from the numerical results are compared with the analytical results of the dilute distribution model and the MT model.

2. Materials and Methods

Simulations were performed based on the known properties of their component base materials. The study material properties were chosen based on previous technical investigations and experiments to provide reliable inputs for the numerical models as follows: i) *Bacillus subtilis* JC3 was identified as a spore-forming aerobic alkaliphilic bacterium. Peptone, NaCl, and yeast extract were used as growth media.

The matrix characteristics for the control and bacterial concrete BC were developed at the age of 28 days, as shown in Table 1, with an optimum *B. Subtilis* cell.

Table 1. Plain and bacterial concrete characteristics

Matrix type	Control concrete CC	Bacterial concrete BC
Density (g/cm ³)	2300	2300
Elastic modulus E (MPa)	32200	36700
Poisson's ratio ν	0.18	0.18
Tensile strength f_t (MPa)	4.51	5.13
Compressive strength f_c (MPa)	52.01	61.06

Subtilis cell concentration equal to 105 cells/ml of mixing water (Rao et al., 2017).

ii) The macro-synthetic polyethylene fibres have a unit diameter d_f , aspect ratio $AR_f = l_f / d_f$, density, elastic modulus E , Poisson's ratio ν , and ultimate tensile strength as shown in Table 2. High-strength fibre/type 1 (Monishaa and Namitha, 2017) and low-strength fibre/type 2 (Bentur and Mindess, 2006) were provided. To investigate the target homogenized characteristics, the synthetic fibre matrix included different volume contents ($v_f = 0.3, 0.5, 0.75, 1, 1.5, 2, 3$, and 4%) for both the M40 control and bacterial concrete. The scheme of the specimen sets used to generate the RVE models is shown in

Figure 1. The generated 34 models were modelled to explore the synergistic effects of bacteria and fibres. For macroscopic simulation and computing the homogenized properties of chopped fibre composites, the study presents numerical RVE modelling of fibrous composite concrete modelled using ANSYS material designer integrated in the ANSYS software package, as shown in Figure 2. The Material designer modelling procedure of a chopped fibre composite is summarized using different parameters until the geometric meshing of the internal shape, as follows: 1) The seed number against which the random fibre directions are calculated.

Table 2. Macro-synthetic fibre characteristics

Fibre type	Type 1	Type 2
Fibre strength type	High	Low
Diameter d_f (μm)	433	625
Aspect ratio AR_f	90	48
Density (g/cm^3)	0.97	0.94
Elastic modulus E_f (MPa)	73000	5000
Poisson's Ratio ν_f	0.422	0.418
Ultimate tensile strength f_{tf} (MPa)	2580	600

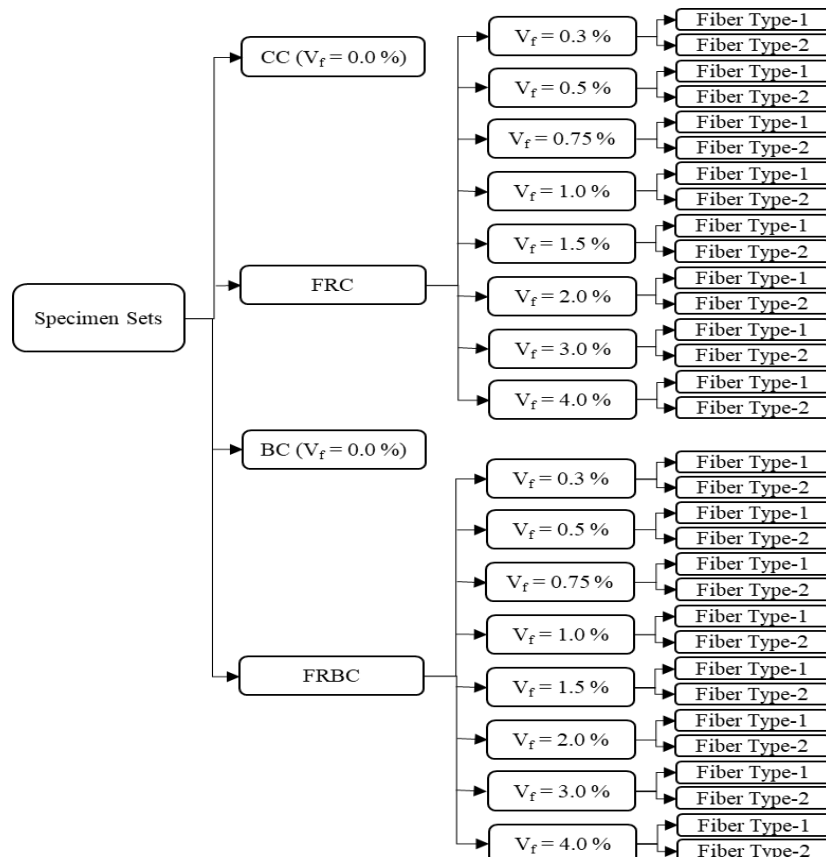


Fig. 1. Scheme of the study specimen sets

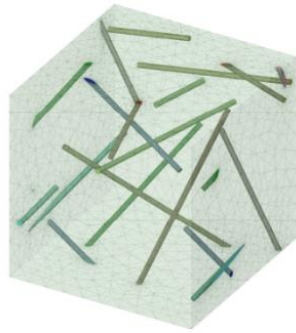


Fig. 2. Meshed chopped fibre composites of ANSYS material designer typical RVE

2) The repeat count specifies whether a given volume is sufficiently large to

represent the number of fibres in the RVE. If the RVE size is insufficient, the software may fail to generate an RVE geometry with self-intersecting fibres that are longer than the RVE size. Consequently, increasing the variable size of the RVE is essential. Table 3 shows the actual numerically corrected size effects for various RVE models.

3) Tensor of symmetric fibre orientation. The initial fibre orientations were specified as uniform in all directions with diagonal values of 0.33, 0.33, 0.33, and zero values for the off-diagonal entries.

Table 3. Actual numerical entries and orientation tensor entries of the RVE geometry

The actual numerical entries for various RVE models						The actual orientation tensor entries of the RVE geometry	
Fibre type	Volume fraction V_f %	Actual V_f %	Seed	Repeat count	No. of fibres /RVE	Diagonal values (a_{11} , a_{22} , a_{33})	Off-diagonal values (a_{12} , a_{13} , a_{23}) and (a_{21} , a_{31} , a_{32})
Type 1	0.0	-	-	-	-	-	-
	0.3	0.3131	1	4	12	0.2632, 0.2502, 0.4866	-0.03205, 0.01635, -0.09209
	0.5	0.5044	1	4	9	0.3616, 0.2778, 0.3606	-0.07518, -0.01506, -0.1615
	0.75	0.8246	1	4	8	0.3191, 0.2141, 0.4668	0.01058, -0.05301, -0.1623
	1	1.11	1	4	7	0.1123, 0.2199, 0.6677	0.039, -0.07615, -0.1813
	1.5	1.641	1	5	11	0.2887, 0.2881, 0.4232	0.083, -0.06024, -0.2119
	2	2.066	1	5	9	0.1458, 0.2446, 0.6096	0.06223, -0.1672, -0.1258
	3	3.17	8	6	13	0.3567, 0.2763, 0.367	0.06598, 0.02428, -0.05158
Type 2	4	4.131	10	6	11	0.2648, 0.4444, 0.2908	-0.05631, 0.01301, -0.2039
	0.0	-	-	-	-	-	-
	0.3	0.3296	1	3	10	0.3147, 0.3333, 0.352	-0.04782, -0.02756, -0.05366
	0.5	0.5673	1	3	8	0.3417, 0.3304, 0.3278	-0.03748, -0.1053, -0.0703
	0.75	0.7694	1	4	14	0.2839, 0.2198, 0.4963	-0.01388, -0.07003, -0.04152
	1	1.015	1	4	12	0.2819, 0.2261, 0.492	0.02245, -0.03927, -0.08307
	1.5	1.511	8	5	19	0.3634, 0.3177, 0.3189	0.04143, -0.04234, 0.03576
	2	2.082	8	5	17	0.4302, 0.2271, 0.3427	0.0165, -0.0994, 0.03733
	3	3.15	8	5	14	0.3587, 0.3012, 0.3401	0.008798, -0.205, 0.03489
	4	4.156	8	5	12	0.2957, 0.402, 0.3024	0.09896, -0.02228, 0.1095

Table 3 shows the actual values of the orientation tensor entries determined after generating the actual RVE geometry size and fibre fractions.

3. Results and Discussion

The dimensional change in fibrous bacterial concrete affects the performance and service life of structures. Excessive loading can lead to cracking, reduced serviceability, and compromised durability, while unexpected cracks can result in structural damage and loss of functionality. A numerical RVE model was used to study the improvement of certain properties, such as the elasticity modulus E_y , shear modulus G_{yz} , Poisson's ratio ν_{xz} , and density ρ . The

mean and Standard Deviation (SD) of results are displayed in Figure 3 with SD below 2.14%. The target samples were mentioned as “matrix type - fibre type”.

With respect to plain concrete, high-strength fibre reinforced concrete FRC-1, bacterial concrete BC, high-strength fibre reinforced bacterial concrete FRBC-1, and low-strength fibre reinforced bacterial concrete FRBC-2, the mean values of elasticity modulus E_{eff} and shear modulus G_{eff} increased by 1.52% and 1.11%, 13.98% and 13.98%, 15.46% and 14.97%, and 11.09% and 10.60%, respectively. The mean values decreased by 2.39% and 2.85% for the low-strength fibre reinforced concrete FRC-2.

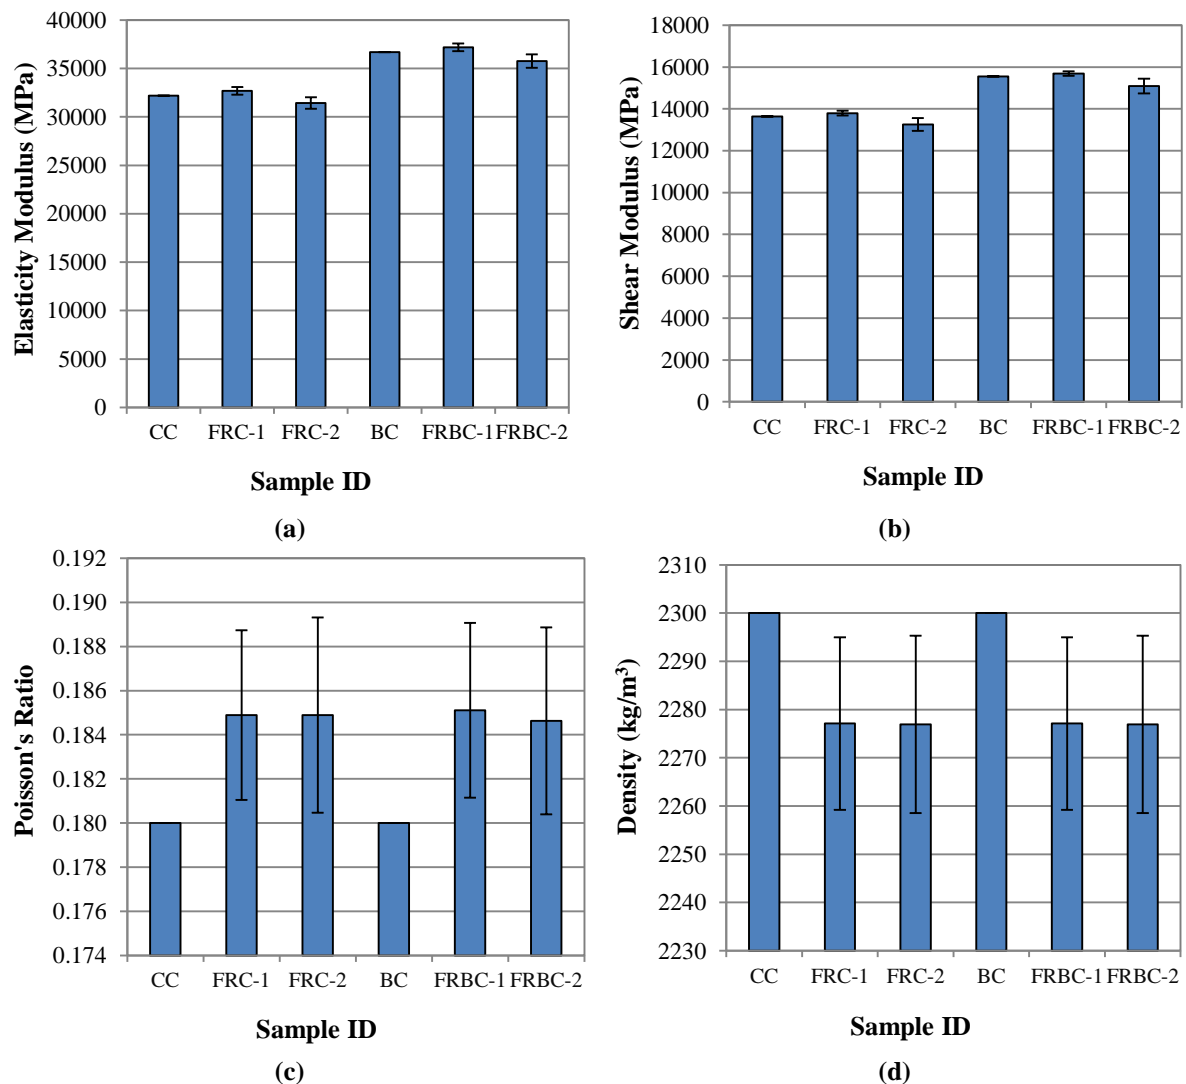


Fig. 3. Concrete properties of the study samples: a) Elasticity modulus; b) Shear modulus; c) Poisson's ratio; and d) Density

Detailed improvements in elasticity and shear moduli for both the FRC and FRBC relative to the M40 conventional concrete are illustrated in Figure 4. The target samples are mentioned as “matrix type - fibre type - homogenized moduli”. The elastic and shear moduli for both the FRC and FRBC increased with the high-strength fibre content, whereas the enhancement in the homogenized moduli decreased with the low-strength fibre content. This innovative result supports the fact that high-strength fibres improve ductility because fibre pull-out is the desired failure mode for dissipating energy in the matrix (Richardson, 2005; Khan and Ayub, 2016).

Polyethylene macro-synthetic fibres can enhance the pre-peak elastic modulus of an element, causing an increase in flexural strength and shear capacity (Pantazopoulou and Zanganeh, 2001; Majdzadeh et al., 2006). Bhosale et al. (2019) concluded that

increasing the energy-absorbing capability during fracture improved post-peak ductility (Bhosale et al., 2019).

Polyethylene macro-synthetic fibres provide post-cracking tensile resistance across cracks (Yıldırım et al., 2015). With respect to plain or bacterial concrete, both high- and low-strength fibre-reinforced concrete and fibre-reinforced bacterial concrete mean values of density decreased by 1%. While high-strength fibre reinforced concrete FRC-1, low-strength fibre reinforced concrete FRC-2, high-strength fibre reinforced bacterial concrete FRBC-1, and low-strength fibre reinforced bacterial concrete FRBC-2, mean values of Poisson's ratio v_{eff} increased by 2.72%, 2.71%, 2.84%, and 2.57%, respectively. The detailed enhancements in Poisson's ratio for FRC and FRBC compared to conventional concrete are illustrated in Figure 5.

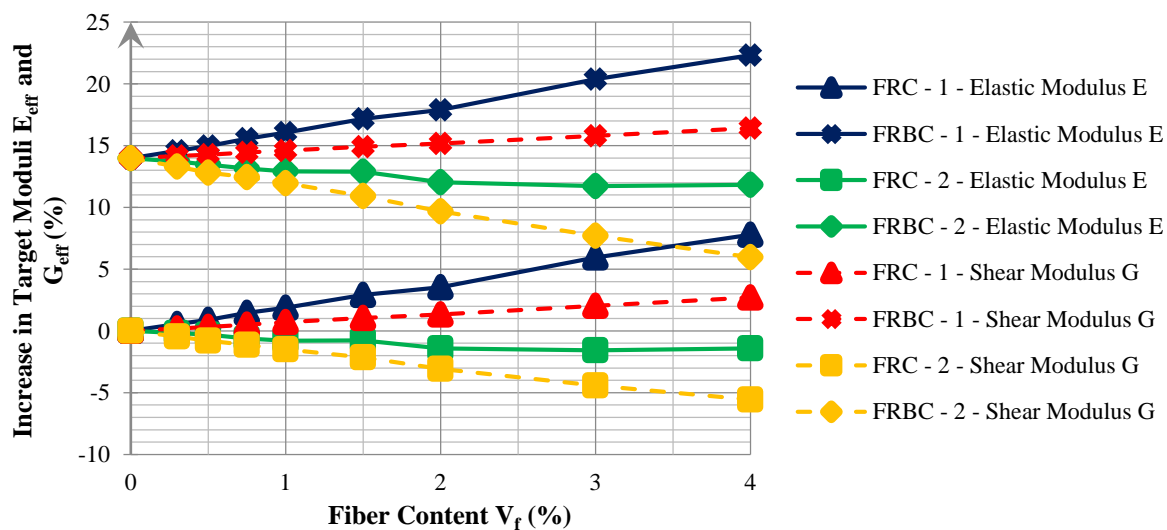


Fig. 4. Enhancement in the target numerical elastic and shear moduli

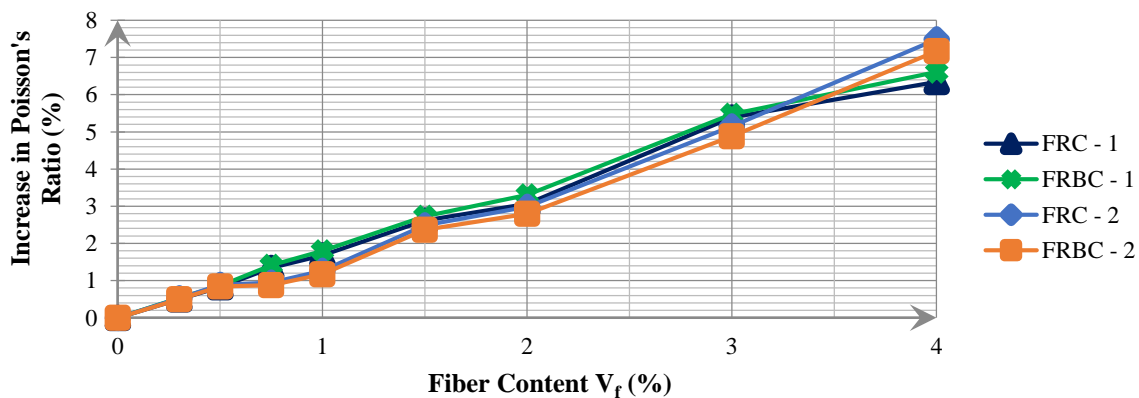


Fig. 5. The enhancement in the target numerical Poisson's ratio, v_{eff}

The Poisson's ratio enhancement increased with the content of high-strength or low-strength fibres in both fibrous concrete and fibrous bacterial concrete, indicating improved crack formation arrest and post-peak strength (Tiberti et al., 2014).

Related to the reference conventional concrete, the results indicated that the inclusion of high-strength fibre from 0% to 2% and constant content of *Bacillus subtilis* bacteria increased the elastic modulus, shear modulus, and Poisson's ratio in the range of 13.98-17.89%, 13.98-15.16%, and 0-3.30%, respectively. However, the inclusion of only high-strength fibre from 0% to 2% without *Bacillus subtilis* bacteria increased the elastic modulus, shear

modulus, and Poisson's ratio in the range of 0-3.54%, 0-1.32%, and 0-2.98%, respectively. Hence, the contribution of *Bacillus subtilis* bacteria distinguished in concrete mixtures with different fibre percentages from 0% to 2% was in the ranges of 13.98-14.35%, 13.98-13.84%, and 0-0.32% for the elastic modulus, shear modulus, and Poisson's ratio, respectively.

One of the current research objectives is to verify the numerical bulk modulus and shear modulus results using the analytical DD and MT models. As depicted in Figures 6 and 7, the homogenized numerical results are in good agreement with the analytical results for the bulk and shear moduli.

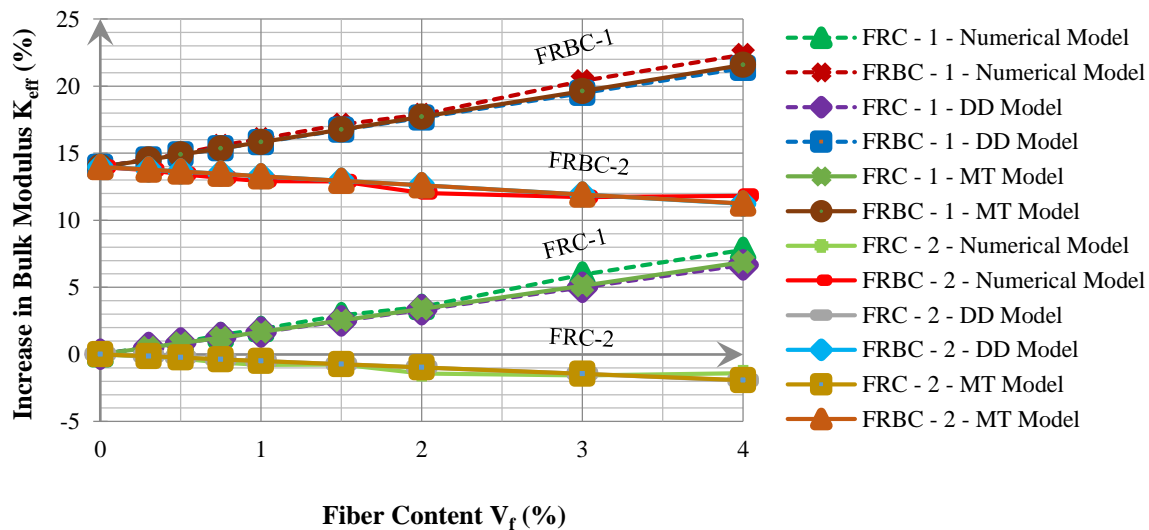


Fig. 6. Validation of target bulk modulus, K_{eff}

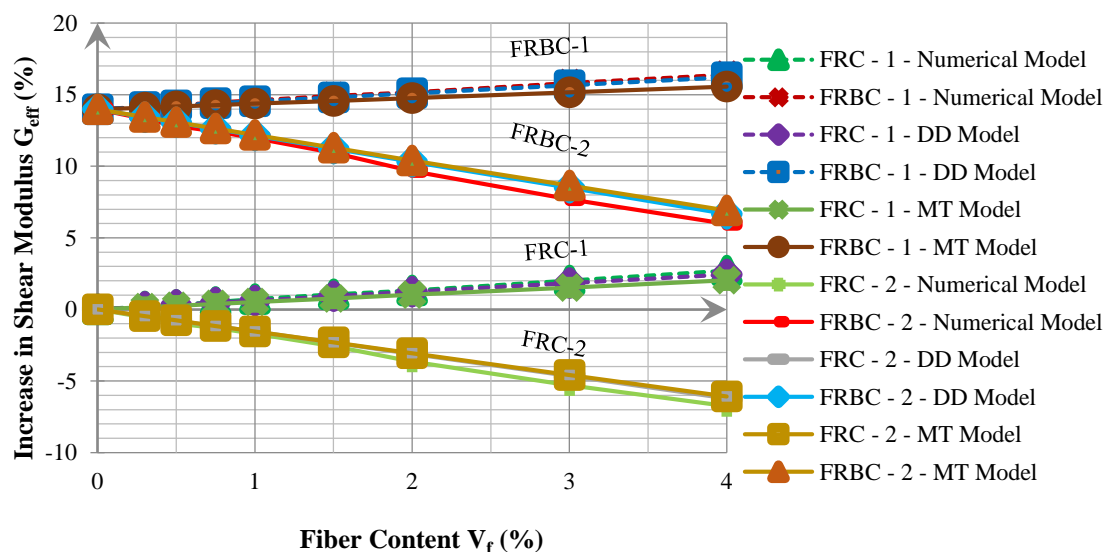


Fig. 7. Validation of target shear modulus, G_{eff}

The target samples are mentioned as “matrix type - fibre type - modelling method”. In addition, the statistical hypothesis factorial ANOVA test in SPSS V25 software was used to compare the effect of analysis methods on composite moduli, finding no significant differences between the numerical and analytical results and no significant differences between FRBC and FRC in terms of poisson’s ratio, but significant differences among different matrix types in elastic and shear moduli. Figure 8 shows target composite properties E_{eff} , G_{eff} , and ν_{eff} that are equal to -0.5%, -1%, and 2.75% for FRC, 13.98%, 13.98%, 0% for BC, and 13.25%, 12.75%, 2.75% for FRBC, respectively, with a 99% confidence level. The mean values show that fibrous FRBC and non-fibrous BC had better elasticity and shear moduli than traditional concrete. The biological self-repairing concept of traditional concrete has more effective advantages, and the addition of high-strength fibres only slightly enhances these properties. This result is broadly consistent with the major trends of other studies, in which the initial tangent modulus E_{it} changed slightly with the addition of fibres (Ezeldin and Balaguru, 1992; Algihtwel, 2018). Fibrous bacterial concrete mitigates dimensional changes through the network incorporation of high-strength fibres, which reduces strain and restrains the concrete

matrix. The bacterial components in synthetic fibrous bacterial concrete, such as calcium carbonate-producing bacteria, play a vital role in mitigating dimensional change cracks by producing calcite crystals as fillers in the microstructure. The controlled crack pattern in synthetic fibrous bacterial concrete improves the bond strength between the fibres and the low-porosity matrix, resulting in enhanced flexural strength and shear capacity. As a result, the biological self-repairing concept of traditional and fibrous concrete achieved more effective advantages for the elastic and shear moduli. These findings are consistent with those of previous studies (Qian et al., 2009; Hao et al., 2018; Feng et al., 2019; Kua et al., 2019; Karimi and Mostofinejad, 2020). Despite its inherent benefits, fibrous bacterial concrete can undergo long-term dimensional changes owing to environmental conditions, chemical reactions, and material properties.

Factors such as high temperature, humidity, and exposure to aggressive chemicals can accelerate the growth of bacteria, leading to an increase in the production of calcite crystals, resulting in dimensional changes. Therefore, laboratory testing techniques, including strain gauges and expansion tests, can help researchers understand the behavior of the material and develop predictive models.

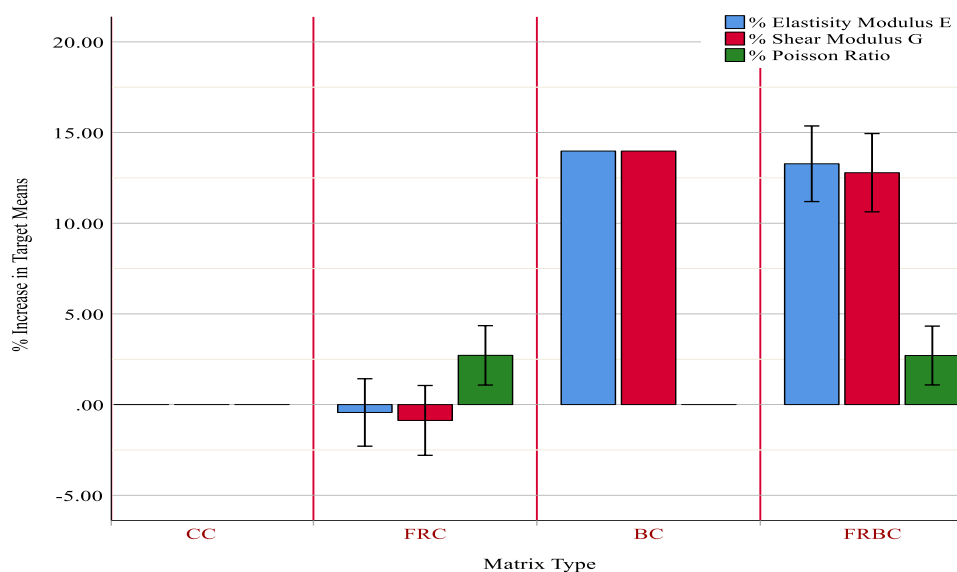


Fig. 8. Enhancement of the properties of different matrix types

Furthermore, as the scope of the investigation expands beyond the prediction of linear elastic properties of composites, the limitations of numerical models become more apparent in modelling post-failure behavior and predicting damage and cracking patterns. Future studies will focus on other dimensional changes of concrete related to the applied loadings as creep deformation, or related to environmental aspects, such as early thermal expansion/contraction and swelling/shrinkage, which account for the majority of cracking in concrete structures.

The fibre parameters, matrix grades, and self-repair techniques require further investigation. In addition, the macroscopic stress, strain distributions, and failure responses require intensive surveys. More data are required to facilitate the design and production of FRBC.

4. Conclusions

The current study investigated the dimensional change properties of concrete that included macro-synthetic fibres and *Bacillus subtilis* bacteria, such as Poisson's ratio, elasticity, and shear moduli. Proper incorporation of fibres and bacteria, coupled with careful mixture design and construction practices, can effectively manage immediate dimensional changes, mitigate long-term dimensional changes, and ensure the optimal performance and longevity of structures constructed using this innovative material. The main findings are as follows: 1) Using high-strength macro-synthetic fibres instead of low-strength synthetic fibres improves the concrete target properties; 2) It is essential to acknowledge that the process of Bacterial-Induced Calcite Precipitation (BICP) involves the conversion of the calcium lactate or urea present in the concrete mixture into calcite, effectively counteracting dimensional changes. The bacterial strain treatment combined with macro-synthetic fibre inclusion increased the conventional concrete homogenized

elastic modulus, shear modulus, and Poisson's ratio properties by 13.25%, 12.75% and 2.75%, respectively, according to the statistical analysis, regardless of the content and mechanical properties of the fibre. Ongoing research has direct positive effects on the design of practical structural elements by developing stronger synthetic fibres and optimizing bacterial activity to further enhance the performance of fibrous bacterial concrete with respect to dimensional changes.

5. References

- Algihwel, M. (2018). "A review on effect of different fiber types on fiber reinforced concrete behavior", *Sustainable Structures and Materials, An International Journal*, 1(2), 36-43, <https://doi.org/10.26392/SSM.2018.01.02.036>.
- Alshalif, A.F., Irwan, J.M., Othman, N., Al-Gheethi, A.A. and Shamsudin, S. (2020). "A systematic review on bio-sequestration of carbon dioxide in bio-concrete systems: a future direction", *European Journal of Environmental and Civil Engineering*, 26(3), 1209-1228, <https://doi.org/10.1080/19648189.2020.1713899>.
- Amjad, H., Arsalan Khushnood, R. and Ali Memon, S. (2023). "Biomimetic robust self-healing of *Bacillus subtilis* immobilized through sisal fiber for next-generation concrete infrastructure", *Construction and Building Materials*, 368(3), 130299, <https://doi.org/10.1016/j.conbuildmat.2023.130299>.
- Bentur, A. and Mindess, S. (2006). *Fibre reinforced cementitious composites*, CRC Press.
- Benveniste, Y. (1987). "A new approach to the application of Mori-Tanaka's theory in composite materials", *Mechanics of Materials*, 6(2), 147-157, [https://doi.org/10.1016/0167-6636\(87\)90005-6](https://doi.org/10.1016/0167-6636(87)90005-6).
- Bhaskar, S. (2021). "Self-healing bacterial cementitious concrete composites: development and performance evaluation", Ph.D. Thesis, Toronto Metropolitan University, <https://doi.org/10.32920/ryerson.14656461.v1>.
- Bhosale, A., Rasheed, M.A., Prakash, S.S. and Raju, G. (2019). "A study on the efficiency of steel vs. synthetic vs. hybrid fibers on fracture behavior of concrete in flexure using acoustic emission", *Construction and Building Materials*, 199, 256-268, <https://doi.org/10.1016/J.CONBUILDMAT.2018.12.011>.
- Chithambar Ganesh, A., Muthukannan, M.,

- Malathy, R. and Ramesh Babu, C. (2019). "An experimental study on effects of bacterial strain combination in fibre concrete and self-healing efficiency", *KSCE Journal of Civil Engineering*, 23(10), 4368-4377, <https://doi.org/10.1007/s12205-019-1661-2>.
- Damodaran, P. and Thangasamy, L. (2023). "Experimental investigation on mechanical properties and characterization of steel fibre concrete with *Bacillus subtilis*", *E3S Web of Conferences*, EDP Sciences, 03002, <https://doi.org/10.1051/e3sconf/2F202338703002>.
- Eshelby, J.D. (1957). "The determination of the elastic field of an ellipsoidal inclusion and related problems", *Proceedings of the Royal Society of London, Series A, Mathematical and Physical Sciences*, 241(1226), 376-396, <https://doi.org/10.1098/rspa.1957.0133>.
- Ezeldin, A.S. and Balaguru, P.N. (1992). "Normal and high-strength fiber-reinforced concrete under compression", *Journal of Materials in Civil Engineering*, 4(4), 415-429, <https://doi.org/10.1061/%28ASCE%290899-1561%281992%294%3A4%28415%29>.
- Feng, J., Su, Y. and Qian, C. (2019). "Coupled effect of pp fiber, pva fiber and bacteria on self-healing efficiency of early-age cracks in concrete", *Construction and Building Materials*, 228, 116810, <https://doi.org/10.1016/j.conbuildmat.2019.116810>.
- Geers, M.G., Kouznetsova, V.G. and Brekelmans, W. (2010). "Multi-scale computational homogenization: trends and challenges", *Journal of computational and applied mathematics*, 234(7), 2175-2182, <https://doi.org/10.1016/j.cam.2009.08.077>.
- Ghoneim, A., Hassan, H. and Aboul-Nour, L. (2020). "Self-repairing polyethylene fiber-reinforced-concrete with *bacillus subtilis* bacteria a review", *International Journal of Engineering and Technology*, 9(2), 437-447, <http://doi.org/10.14419/ijet.v9i2.30172>.
- Ghoniem, A., Hassan, H. and Aboul-Nour, L. (2021). "Behavior of macro-synthetic fiber-reinforced high-strength concrete beams incorporating *bacillus subtilis* bacteria", *Latin American Journal of Solids and Structures*, 18, 1-14, <https://doi.org/10.1590/1679-78256378>.
- Hameed, N.A., Othman, F.M. and Abdul-Hamead, A.A. (2023). "Integration of fdm and self-healing technology: evaluation of crack sealing by durability and mechanical strength", *Materials Research Express*, 10(12), 125701, <https://doi.org/10.1088/2053-1591/2Fad0c7d>.
- Hao, Y., Cheng, L., Hao, H. and Shahin, M.A. (2018). "Enhancing fiber/matrix bonding in polypropylene fiber reinforced cementitious composites by microbially induced calcite precipitation pre-treatment", *Cement and Concrete Composites*, 88, 1-7, <https://doi.org/10.1016/j.cemconcomp.2018.01.001>.
- Hasan, A., Maroof, N. and Ibrahim, Y. (2019). "Effects of polypropylene fiber content on strength and workability properties of concrete", *Polytechnic Journal*, 9(1), 7-12, <https://doi.org/10.25156/PTJ.V9N1Y2019.PP7-12>.
- Jawhar, A.A., Al-Hadithi, A.I. and Mansoor, Y.A. (2024). "An experimental investigation of mechanical properties of wet-mixed shotcrete reinforced with different types of plastic fiber", *AIP Conference Proceedings*, AIP Publishing, <https://doi.org/10.1063/5.0190540>.
- Jena, S., Basa, B. and Panda, K. (2020). "Bacterial concrete for the development of sustainable construction-a review", *Recent Trends in Civil Engineering: Select Proceedings of ICRTICE 2019*, 587-600, <https://doi.org/10.1007/978-981-15-5195-646>.
- Karimi, N. and Mostofinejad, D. (2020). "*Bacillus subtilis* bacteria used in fiber reinforced concrete and their effects on concrete penetrability", *Construction and Building Materials*, 230, 117051, <https://doi.org/10.1016/j.conbuildmat.2019.117051>.
- Khan, S.U. and Ayub, T. (2016). "Modelling of the pre and post-cracking response of the pva fibre reinforced concrete subjected to direct tension", *Construction and Building Materials*, 120, 540-557, <https://doi.org/10.1016/j.conbuildmat.2016.05.130>.
- Kua, H.W., Gupta, S., Aday, A.N. and Srubar, W.V. (2019). "Biochar-immobilized bacteria and superabsorbent polymers enable self-healing of fiber-reinforced concrete after multiple damage cycles", *Cement and Concrete Composites*, 100, 35-52, <https://doi.org/10.1016/j.cemconcomp.2019.03.017>.
- Monishaa, M. and Namitha, S.T. (2017). "Experimental study on strength of self-healing concrete", *SSRG International Journal of Civil Engineering- (ICRTCETM-2017)* (Special Issue), 476-484, <https://www.internationaljournalssrg.org/uploads/specialissuepdf/ICRTCETM/2017/CE/IJCE-ICRTCETM-P189.pdf>.
- Majdzadeh, F., Soleimani, S.M. and Banthia, N. (2006). "Shear strength of reinforced concrete beams with a fiber concrete matrix", *Canadian Journal of Civil Engineering*, 33(6), 726-734, <https://doi.org/10.1139/L05-118>.
- Merli, R., Preziosi, M., Acampora, A., Lucchetti, M.C. and Petrucci, E. (2019). "Recycled fibers in reinforced concrete: A systematic literature

- review", *Journal of Cleaner Production*, 248, 119207, <https://doi.org/10.1016/j.jclepro.2019.119207>.
- Montero-Chacón, F., Sanz-Herrera, J.A. and Doblaré, M. (2019). "Computational multiscale solvers for continuum approaches", *Materials*, 12(5), 691, <https://doi.org/10.3390/ma12050691>.
- Naili, C., Doghri, I., Kanit, T., Sukiman, M.S., Aissa-Berraies, A. and Imad, A. (2020). "Short fiber reinforced composites: Unbiased full-field evaluation of various homogenization methods in elasticity", *Composites Science and Technology*, 187, 107942, <https://doi.org/10.1016/j.compscitech.2019.107942>.
- Pantazopoulou, S.J. and Zanganeh, M. (2001). "Triaxial tests of fiber-reinforced concrete", *Journal of Materials in Civil Engineering*, 13(5), 340-348, <https://doi.org/10.1061/%28ASCE%290899-1561%282001%2913%3A5%28340%29>.
- Qian, S., Zhou, J., De Rooij, M., Schlangen, E., Ye, G. and Van Breugel, K. (2009). "Self-healing behavior of strain hardening cementitious composites incorporating local waste materials", *Cement and Concrete Composites*, 31(9), 613-621, <https://doi.org/10.1016/j.cemconcomp.2009.03.003>.
- Raju, K., Tay, T.E. and Tan, V.B.C. (2021). "A review of the fe2 method for composites", *Multiscale and Multidisciplinary Modeling, Experiments and Design*, 4, 1-24, <https://doi.org/10.1007/s41939-020-00087-x>.
- Rameshkumar, V., Prabhath Ranjan Kumar, S., Poornima, V., Venkatasubramani, R. and Sreevidya, V. (2020). "Improvements in mechanical and durability parameters of bio-engineered concrete with metakaolin as a partial substitute for cement", *European Journal of Environmental and Civil Engineering*, 1-14, <https://doi.org/10.1080/19648189.2020.1767696>.
- Rao, M.V.S., Reddy, V.S. and Sasikala, C. (2017). "Performance of microbial concrete developed using bacillus subtilis JC3", *Journal of The Institution of Engineers (India): Series A*, 98(4), 501-510, <https://doi.org/10.1007/s40030-017-0227-x>.
- Richardson, A. (2005). "Bond characteristics of structural polypropylene fibres in concrete with regard to post-crack strength and durable design", *Structural Survey*, 23(3), 210-230, <https://doi.org/10.1108/02630800510610143>.
- Tiberti, G., Minelli, F., Plizzari, G.A. and Vecchio, F.J. (2014). "Influence of concrete strength on crack development in SFRC members", *Cement and Concrete Composites*, 45, 176-185, <https://doi.org/10.1016/j.cemconcomp.2013.10.004>.
- Tiwari, P.K. and Singh, V.K. (2024). "Assessment of polypropylene fiber for effect on fresh and physical performance with durability of self-compacted recycled aggregate concrete", *Civil Engineering Infrastructures Journal*, 58(1), 15-34, <https://doi.org/10.22059/cej.2024.362561.1943>.
- Vijay, K., Murmu, M. and Deo, S.V. (2017). "Bacteria based self-healing concrete - a review", *Construction and Building Materials*, 152(Supplement C), 1008-1014, <https://doi.org/10.1016/j.conbuildmat.2017.07.040>.
- Wang, J., Dewanckele, J., Cnudde, V., Van Vlierberghe, S., Verstraete, W. and De Belie, N. (2014). "X-ray computed tomography proof of bacterial-based self-healing in concrete", *Cement and Concrete Composites*, 53, 289-304, <https://doi.org/10.1016/j.cemconcomp.2014.07.014>.
- Wiktor, V. and Jonkers, H.M. (2011). "Quantification of crack-healing in novel bacteria-based self-healing concrete", *Cement and Concrete Composites*, 33(7), 763-770, <https://doi.org/10.1016/j.cemconcomp.2011.03.012>.
- Yıldırım, G., Keskin, Ö.K., Keskin, S.B., Şahmaran, M. and Lachemi, M. (2015). "A review of intrinsic self-healing capability of engineered cementitious composites: recovery of transport and mechanical properties", *Construction and Building Materials*, 101, 10-21, <https://doi.org/10.1016/j.conbuildmat.2015.10.018>.
- Yoo, D.Y. and Moon, D.Y. (2018). "Effect of steel fibers on the flexural behavior of rc beams with very low reinforcement ratios", *Construction and Building Materials*, 188, 237-254, <https://doi.org/10.1016/j.conbuildmat.2018.08.099>.
- Zhang, W., Zheng, Q., Ashour, A. and Han, B. (2020). "Self-healing cement concrete composites for resilient infrastructures: A review", *Composites Part B: Engineering*, 189, 107892, <https://doi.org/10.1016/j.compositesb.2020.107892>.



This article is an open-access article distributed under the terms and conditions of the Creative Commons Attribution (CC-BY) license.